

AD-A139 174

ELECTROCHEMICAL POLYMERIZATION OF PYRROLE AND
ELECTROCHEMISTRY OF POLYPYR..(U) STATE UNIV OF NEW YORK
AT BUFFALO DEPT OF CHEMISTRY P G PICKUP ET AL. JAN 84


1/1


UNCLASSIFIED

SUNYBUF/DC/TR-16 N00014-79-C-0682

F/G 7/4

NL

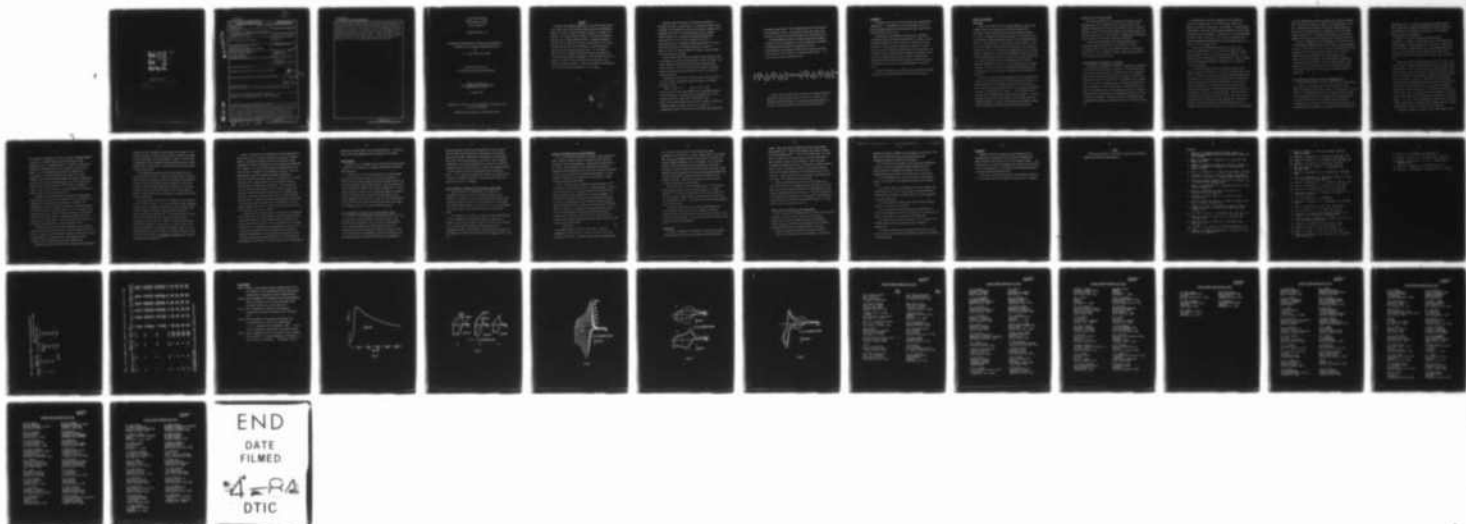

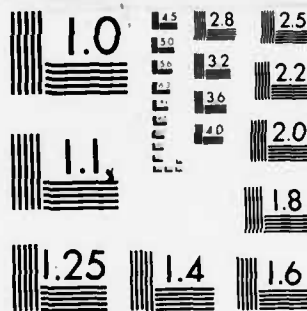

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER SUNYBUF/DC/TR-16	2. GOVT AC. ESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Electrochemical Polymerization of Pyrrole And Electrochemistry of Polypyrrole Films in Ambient Temperature Molten Salts		5. TYPE OF REPORT & PERIOD COVERED
7. AUTHOR(s) P.G. Pickup and R.A. Osteryoung		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry State University of New York at Buffalo Buffalo, New York 14214		8. CONTRACT OR GRANT NUMBER(s) NR-051-715
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Chemistry Program Arlington, VA 22117		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE January, 1984
		13. NUMBER OF PAGES 30
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release: Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) MAR 21 1984		
18. SUPPLEMENTARY NOTES Prepared for publication in The Journal of The American Chemical Society		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Molten Salts; Electropolymerization; Modified Electrodes		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Oxidative electrochemical polymerization of pyrrole has been shown to occur in the 1:1 mole ratio $AlCl_3$:N-(1-butyl)pyridinium chloride (BuPyCl) molten salt at 40°C. Polypyrrole cannot be prepared in analogous 0.8:1 (basic) or 1.2:1 (acidic) mole ratio melts. The polypyrrole prepared in the molten salt is electrochemically similar to polypyrrole prepared in acetonitrile; both		

DD FORM 1473 1 JAN 73 EDITION OF 1 NOV 83 IS OBSOLETE

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

84 03 20 012

AD A139174

DTIC FILE COPY

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

materials are conductors when oxidized, can be used as electrode materials for the electrochemistry of solution species (eg ferrocene) and are oxidized and reduced at ca . -200 mV vs SCE in CH_3CN . The cyclic voltammetry of materials prepared in both CH_3CN and in the neutral melt has been investigated in the $\text{AlCl}_3\text{:BuPyCl}$ molten salt system and in CH_3CN . The most significant differences appear in the kinetics of the redox chemistry. The most facile behavior was observed in a 0.8:1 melt with polypyrrole prepared in the 1:1 melt.

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

OFFICE OF NAVAL RESEARCH

Contract N00014-79-C-0682

Task No. NR-051-715

TECHNICAL REPORT NO. 16

ELECTROCHEMICAL POLYMERIZATION OF PYRROLE AND ELECTROCHEMISTRY OF
POLYPYRROLE FILMS IN AMBIENT TEMPERATURE MOLTEN SALTS

by

P.G. Pickup and R.A. Osteryoung

Prepared for Publication in
The Journal of The American Chemical Society

Department of Chemistry
State University of New York at Buffalo
Buffalo, New York 14214

January, 1984

Reproduction in whole or in part is permitted for any purpose of the
United States Government

Approved for Public Release: Distribution Unlimited


Oxidative electrochemical polymerization of pyrrole has been shown to occur in the 1:1 mole ratio $\text{AlCl}_3\text{:N-(1-butyl)pyridinium chloride (RuPyCl)}$ molten salt at 40°C . Polypyrrole cannot be prepared in analogous 0.8:1 (basic) or 1.2:1 (acidic) mole ratio melts. The polypyrrole prepared in the molten salt is electrochemically similar to polypyrrole prepared in acetonitrile; both materials are conductors when oxidized, can be used as electrode materials for the electrochemistry of solution species (eg ferrocene) and are oxidized and reduced at ca . -200 mV vs SSCE in CH_3CN . The cyclic voltammetry of materials prepared in both CH_3CN and in the neutral melt has been investigated in the $\text{AlCl}_3\text{:RuPyCl}$ molten salt system and in CH_3CN . The most significant differences appear in the kinetics of the redox chemistry. The most facile behavior was observed in a 0.8:1 melt with polypyrrole prepared in the 1:1 melt.

1. DESCRIPTION FOR
 2. APPROX. QUANTITY
 3. UNIT PRICE
 4. AMOUNT
 5. DATE OF RECEIPT
 6. REMARKS
 7. INITIALS
 8. SIGNATURE
 9. DATE
 10. REMARKS
 11. INITIALS
 12. SIGNATURE
 13. DATE
 14. REMARKS
 15. INITIALS
 16. SIGNATURE
 17. DATE
 18. REMARKS
 19. INITIALS
 20. SIGNATURE
 21. DATE
 22. REMARKS
 23. INITIALS
 24. SIGNATURE
 25. DATE
 26. REMARKS
 27. INITIALS
 28. SIGNATURE
 29. DATE
 30. REMARKS
 31. INITIALS
 32. SIGNATURE
 33. DATE
 34. REMARKS
 35. INITIALS
 36. SIGNATURE
 37. DATE
 38. REMARKS
 39. INITIALS
 40. SIGNATURE
 41. DATE
 42. REMARKS
 43. INITIALS
 44. SIGNATURE
 45. DATE
 46. REMARKS
 47. INITIALS
 48. SIGNATURE
 49. DATE
 50. REMARKS
 51. INITIALS
 52. SIGNATURE
 53. DATE
 54. REMARKS
 55. INITIALS
 56. SIGNATURE
 57. DATE
 58. REMARKS
 59. INITIALS
 60. SIGNATURE
 61. DATE
 62. REMARKS
 63. INITIALS
 64. SIGNATURE
 65. DATE
 66. REMARKS
 67. INITIALS
 68. SIGNATURE
 69. DATE
 70. REMARKS
 71. INITIALS
 72. SIGNATURE
 73. DATE
 74. REMARKS
 75. INITIALS
 76. SIGNATURE
 77. DATE
 78. REMARKS
 79. INITIALS
 80. SIGNATURE
 81. DATE
 82. REMARKS
 83. INITIALS
 84. SIGNATURE
 85. DATE
 86. REMARKS
 87. INITIALS
 88. SIGNATURE
 89. DATE
 90. REMARKS
 91. INITIALS
 92. SIGNATURE
 93. DATE
 94. REMARKS
 95. INITIALS
 96. SIGNATURE
 97. DATE
 98. REMARKS
 99. INITIALS
 100. SIGNATURE
 101. DATE
 102. REMARKS
 103. INITIALS
 104. SIGNATURE
 105. DATE
 106. REMARKS
 107. INITIALS
 108. SIGNATURE
 109. DATE
 110. REMARKS
 111. INITIALS
 112. SIGNATURE
 113. DATE
 114. REMARKS
 115. INITIALS
 116. SIGNATURE
 117. DATE
 118. REMARKS
 119. INITIALS
 120. SIGNATURE
 121. DATE
 122. REMARKS
 123. INITIALS
 124. SIGNATURE
 125. DATE
 126. REMARKS
 127. INITIALS
 128. SIGNATURE
 129. DATE
 130. REMARKS
 131. INITIALS
 132. SIGNATURE
 133. DATE
 134. REMARKS
 135. INITIALS
 136. SIGNATURE
 137. DATE
 138. REMARKS
 139. INITIALS
 140. SIGNATURE
 141. DATE
 142. REMARKS
 143. INITIALS
 144. SIGNATURE
 145. DATE
 146. REMARKS
 147. INITIALS
 148. SIGNATURE
 149. DATE
 150. REMARKS
 151. INITIALS
 152. SIGNATURE
 153. DATE
 154. REMARKS
 155. INITIALS
 156. SIGNATURE
 157. DATE
 158. REMARKS
 159. INITIALS
 160. SIGNATURE
 161. DATE
 162. REMARKS
 163. INITIALS
 164. SIGNATURE
 165. DATE
 166. REMARKS
 167. INITIALS
 168. SIGNATURE
 169. DATE
 170. REMARKS
 171. INITIALS
 172. SIGNATURE
 173. DATE
 174. REMARKS
 175. INITIALS
 176. SIGNATURE
 177. DATE
 178. REMARKS
 179. INITIALS
 180. SIGNATURE
 181. DATE
 182. REMARKS
 183. INITIALS
 184. SIGNATURE
 185. DATE
 186. REMARKS
 187. INITIALS
 188. SIGNATURE
 189. DATE
 190. REMARKS
 191. INITIALS
 192. SIGNATURE
 193. DATE
 194. REMARKS
 195. INITIALS
 196. SIGNATURE
 197. DATE
 198. REMARKS
 199. INITIALS
 200. SIGNATURE
 201. DATE
 202. REMARKS
 203. INITIALS
 204. SIGNATURE
 205. DATE
 206. REMARKS
 207. INITIALS
 208. SIGNATURE
 209. DATE
 210. REMARKS
 211. INITIALS
 212. SIGNATURE
 213. DATE
 214. REMARKS
 215. INITIALS
 216. SIGNATURE
 217. DATE
 218. REMARKS
 219. INITIALS
 220. SIGNATURE
 221. DATE
 222. REMARKS
 223. INITIALS
 224. SIGNATURE
 225. DATE
 226. REMARKS
 227. INITIALS
 228. SIGNATURE
 229. DATE
 230. REMARKS
 231. INITIALS
 232. SIGNATURE
 233. DATE
 234. REMARKS
 235. INITIALS
 236. SIGNATURE
 237. DATE
 238. REMARKS
 239. INITIALS
 240. SIGNATURE
 241. DATE
 242. REMARKS
 243. INITIALS
 2

Electrodes coated with polymer films have been the subject of considerable interest in recent years (1). An especially important class of polymers in this respect are electronically conducting polymers such as polypyrrole (PP) (2-16). PP coatings have been used as an organic electrode material (7), to protect semiconductor electrodes from photocorrosion (17) as an "ion gate" membrane (18-20) and in electrocatalysis (21). An important potential application of PP is as a charge storing material in rechargeable batteries. However, in CH_3CN , in which PP is normally prepared and studied, long term stability and charging rates are problems.

We have recently shown (22) that a number of redox polymers as films on electrodes can be rapidly electrochemically oxidized and reduced in the ambient temperature molten salt system $\text{AlCl}_3/\text{N}-(1\text{-butyl})\text{pyridinium}$ chloride (BuPyCl). Since this solvent system is viewed as a promising material for batteries we were interested in using it as a medium for PP electrochemistry.


Mixtures of AlCl_3 and BuPyCl in the mole ratios 0.75:1 through 2:1 are ionic liquids at temperatures above 27°C (23,24). The dominant equilibrium is (25):



and the 1:1 melt is almost pure BuPyAlCl₄ with a considerable amount of ion pairing (27,28). Any AlCl_3 (a Lewis acid) added to the 1:1 melt complexes with AlCl_4^- to form AlCl_7^- and the melt is then acidic. When the AlCl_3 :BuPyCl mole ratio is 2:1 the melt is almost pure BuPyAl₂Cl₇. Addition of BuPyCl to the 1:1 melt results in a corresponding increase in free chloride ion (a Lewis base) concentration

and the melt becomes basic. Thus the Lewis basicity (pCl) of the melt can be varied between 0 and 19. In this work we use the neutral melt (mole ratio=1:1), two basic melts (0.8:1 and 0.95:1) and an acidic melt (1.2:1).

The electrochemical oxidation of pyrrole in acetonitrile produces a polypyrrole film on the electrode (2). When the electrode is transferred to a CH₃CN/electrolyte solution the polypyrrole film can be electrochemically driven between the black, highly conducting (100 ohm⁻¹ cm⁻¹) oxidized form and the yellow, non-conducting neutral form. This redox reaction has been characterized as (R):

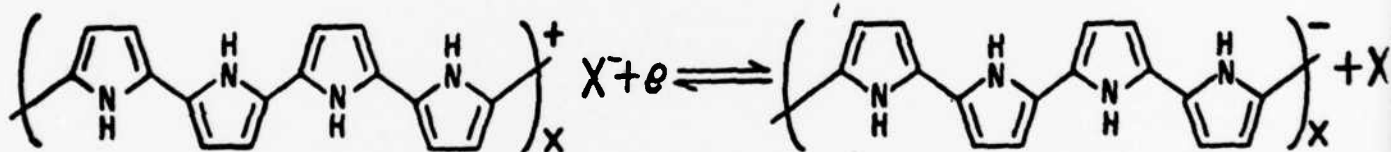

We have found, and report here, that pyrrole can be electrochemically polymerized in neutral melt (but not in 0.8:1 nor 1.2:1 melts) to form conducting films on electrodes. We also describe the electrochemistry of PP films in pure melts and melts containing electroactive species.

EXPERIMENTAL

The preparation and use of the melts used here have been described elsewhere (24). All experiments in melts were performed at 40°C in a Vacuum Atmospheres Company dry box under purified argon. Experiments in CH₃CN were performed at 25 ± 5°C.

Electrochemical experiments were performed using an IRM EC/225 Voltammetric analyzer and a Hewlett Packard 7046A X-Y recorder. A NaCl saturated SCE (SSCE) was used for experiments in CH₃CN and an Al wire immersed in 2:1 melt was used as the reference electrode in the melt. Using ferrocene as an internal reference the Al wire was found to be +110 mV relative to SSCE in CH₃CN (The formal potential of ferrocene is +270 mV vs Al in the melt system and +380 mV vs SSCE in CH₃CN). Working electrodes were either glassy carbon of geometric area 0.071 cm² sealed in Pyrex glass, Pt wire (area = 0.0079 cm²) shrouded in Teflon or Pt foil.

Pyrrole was purified on a dry alumina column: Acetonitrile (Burdick and Jackson; UV grade) and Et₄NClO₄ (Baker) were used as received.

RESULTS AND DISCUSSION

Film Growth.

In neutral melt pyrrole (0.17 M) oxidation begins at ca. $+0.5\text{V}$ and the peak current occurs at ca. $+1.2\text{V}$ at both glassy carbon and Pt electrodes. Polymer films were grown by setting the potential between $+0.7\text{V}$ and $+0.9\text{V}$ (depending on the required growth rate), switching on the cell, allowing a measured quantity of charge to flow and then switching off the cell. A typical current vs. time profile is shown in Figure 1. After the initial charging current the current falls and then rises to a peak as the film begins to grow. The current then gradually falls as the film gets thicker. The peak time varies from one experiment to the next and the rate of current decrease after the peak is variable but the overall shape of the i vs. t plot is the same for C and Pt electrodes and for different potentials between $+0.7\text{V}$ and $+0.9\text{V}$. On Pt, film growth can be verified by inspection: very thin films ($<50 \text{ nm}$) are brown and transparent, thicker films are black. On C, film growth is verified by cyclic voltammetry in pure melt.

In 0.8:1 melt (basic) containing pyrrole (0.17 M) an oxidation wave begins at $+0.5\text{V}$ but attempts to grow PP films from this melt failed. The oxidation current at $+0.7\text{V}$ decreased continually with time showing no peak. Failure to grow polymer from this melt is not surprising considering the high Cl^- concentration (ca. 0.9 M). In the 0.8:1 melt pyrrole oxidation and Cl^- oxidation occur at about the same potential. Bard and coworkers (13) have shown that oxidation of Cl^- at PP coated electrodes destroys the polymer. Diaz et al (2) reported that nucleophilic species inhibit PP formation and we have found that LiCl prevents pyrrole

polymerization in 99% aqueous CH_3CN .

In 1.2:1 melt (acidic) only a very small pyrrole (0.17 M) wave was observed at ca. $+1.2\text{V}$. The peak current at C was only 1/40th of that observed in the neutral melt and at Pt the current was down by a factor of over 250. In fact, at Pt the pyrrole oxidation was hardly discernable. No PP films could be grown from the 1.2:1 melt. Presumably pyrrole forms some adduct with AlCl_3 in the acid melt which cannot be oxidized.

In view of the above results, all films (except those grown in CH_3CN) were prepared in neutral melt (the criterion for a neutral $\text{AlCl}_3/\text{BuPyCl}$ melt is that the electrochemical window at C is at least -1V to $+2\text{V}$ (29)). PP can be prepared in slightly basic melt (eg 0.99:1) but such films were not used in this work.

Cyclic voltammetry of polypyrrole in pure melts.

Polypyrrole coated electrodes, prepared in a neutral melt, were washed with neutral melt and their cyclic voltammetry in a neutral melt and then in a 0.8:1 melt, neither containing dissolved pyrrole, was investigated. Figure 2A shows the first scan (at 100 mV/s) for a ca. 0.2 microns thick (see below) PP film on C in neutral melt. On subsequent scans the cathodic peak at -0.77V quickly disappeared (after 4 scans) and was replaced by a small cathodic peak at -0.94V which shifted to -0.80V during the next 20 scans. The cathodic peak at -0.36V increased during the first 8 scans and then decreased. The anodic peak at 0V increased during the first 4 scans and then it too decreased. After ca. 20 scans the voltammograms showed little change on subsequent scans and the 20th scan is also shown in Figure 2A.

By comparison with the cyclic voltammetry of PP in CH_3CN (8) we interpret the cathodic wave at -0.36 V and the anodic wave at 0 V as reduction and oxidation, respectively, of the polymer. The large charging current anodic of this redox couple has been interpreted as indicating that the oxidized form of the polymer is a conductor (13). We have not assigned the cathodic waves in the region -0.7 V to -1 V but we believe that they could be associated with the known proton containing species impurity in the melt or with trace oxygen (30).

When the above electrode was transferred to 0.8:1 melt and its potential scanned between -1 V and $+0.3\text{ V}$ at 100 mV/s cathodic and anodic peaks developed at -0.44 V and -0.05 V respectively (Figure 2R). A small cathodic wave at -0.85 V was seen only on the first scan. After all changes in the voltammogram were complete the voltammogram at 5 mV/s shown in Figure 2C was obtained.

We interpret the above behavior and the gradual decrease in the polymer redox waves in neutral melt in terms of the solvent content of the polymer. Oxidation and reduction of the polymer require that anions enter and leave the film or that cations leave and enter the film respectively. These ion movements and hence oxidation and reduction of the film are presumably facilitated by incorporation of the melt into the polymer (solvent swelling) (31,32). Since the polymer was prepared in a melt we can assume that initially it contained some melt. The gradual loss of redox activity in the neutral melt could be due to loss of melt from the film (deswelling) producing a more compact polymer with restricted ion mobility. The return of activity in basic melt would then be due to chloride ions which, being the smallest ion in the melts, would be expected

to have the highest mobility within the polymer (33) (contrary to bulk melt (34)). This explains the great improvement in the oxidation wave in basic melt. Oxidation requires movement of anions into a neutral polymer (or cations out of the polymer) and thus is expected to exhibit the greatest kinetic limitations (31). The break-in period observed in the basic melt suggests that more melt is being incorporated into the polymer (22,31,32).

The cyclic voltammetry of PP on Pt electrodes is very similar to that on C electrodes but appears to be more facile. Figure 3 shows voltammograms of a ca. 0.2 micron film of PP on Pt in 0.8:1 melt after potential cycling in the neutral melt and then break-in in the basic melt. The linear dependence of i_p on scan speed and the average i_p/i_c of 0.95 indicate that the redox reaction is facile and almost electrochemically reversible under these conditions. The small constant cathodic current between -0.5V and -1V is presumably due to a proton containing species which diffuses through the PP film (33) to the Pt electrode where it is reduced (30).

Film thickness and analysis of the cyclic voltammetry of PP.

Estimation of the amount of pyrrole in the PP films and the thickness of the films is not straightforward. For films prepared in CH₃CN a number of approaches have been taken. Diaz et al (5,8) measured an n value of 2.25 for the polymerization reaction and estimated the film thickness from the charge passed during film preparation and the measured density (1.5g cm⁻³) of the film. Their results were supported by measured thicknesses of thick films (ca. 20 microns) and by the observation that the area under the voltammogram of a PP coated electrode corresponds to 9%

(theoretically 11% if $n = 2.25$) of the charge used to prepare the film. Thus it appears that in CH_3CN the polymerization involves 2 electrons per pyrrole molecule and 0.25 electrons per pyrrole unit in the polymer to oxidize the film (as in equation 1).

However, the literature contains other thickness/charge relationships. To produce a 1 micron thick film on a 1 cm^2 electrode the following charges (mC) are suggested: 0.38 (7), 30 (9), 80 400 (10), 240 (4,13) and 400 (8). Presumably the yield of polymer depends upon factors that are not controlled (such as cell design) and so it does not seem advisable to estimate film thicknesses from the charge used to prepare the film.

Perhaps the best way to estimate the quantity of PP in a film is from the area under a slow scan cyclic voltammogram of the film. However, there are two problems. Firstly, the shape of the PP voltammogram (Fig 3), with a small charging current on one side and a large one on the other, makes it difficult to decide what area to measure. Secondly, the charge per pyrrole unit in the polymer is not certain. These two problems are intimately related since the voltammogram merely reflects charging of the polymer film (plus a small constant charging current for the underlying electrode). There seems to be the misconception in the literature that the anodic and cathodic waves at ca. -0.2V correspond to the redox reaction of the polymer and the large currents anodic of these waves are "background" and should be ignored. Any current in the voltammogram that cannot be attributed to the underlying electrode nor to dissolved redox species must be due to charging and hence formal oxidation or reduction of the polymer film.

One would not expect PP to exhibit a typical redox polymer surface

wave (35-39) since presumably it consists of chains or conjugated segments of chains with a range of lengths and hence with different formal potentials (6,16). (A conjugated segment is a section of a chain that is electronically isolated from the rest of the chain by a bend, twist or defect.) It is not reasonable to assume that PP consists of non-interacting or only weakly interacting redox sites with one formal potential. The inverse relationship between chain length and anodic peak potential found for pyrrole oligomers ($E_{pa,N} = 1.35/N - 0.15$ (6,16)) gives some indication of the distribution of E^0 values for the segments of polymer. There is some evidence (6) that these segments are predominantly short, possibly only 5-10 pyrrole units long.

The problem of multiple oxidations and reductions of these segments makes theoretical simulations of this model difficult but intuitively it is compatible with the observed cyclic voltammetry. The peaks in the voltammogram correspond to oxidation and reduction of the longer segments whose formal potentials are bunched together by the $1/N$ relationship; the large "charging current" anodic of the peaks corresponds to primary redox reactions of the shorter segments and secondary and higher order redox reactions of the longer segments. Thus the average charge per pyrrole unit must be potential dependent at all potentials anodic of $-0.5V$.

The alternate and previously assumed explanation for the "charging currents" anodic of the main redox waves is that the oxidized form of PP is similar to a porous metal and that these currents are double-layer charging currents of the PP. This model has been investigated by Bard and co-workers (13) and theoretically formulated by Feldberg (15).

The relative validity of these two models depends upon the microscopic

structure of the PP when immersed in and swollen by the solvent. If the swollen PP consists of chains of PP which are each in contact with solvent, then the former model is the more appropriate. However, if the PP chains are arranged in fibres of diameter large relative to the size of a pyrrole molecule, which are impervious to the solvent then the porous metal model is more reasonable (15).

At this stage we cannot say which model best describes PP in the molten salts used in this work. However, the break-in behavior observed in the basic melt, the sensitivity of the PP electrochemistry to chloride ion concentration and the differences between PP prepared in a melt and PP prepared in CH_3CN (see below) suggest that in the melts PP is non-rigid and contains pores of molecular dimensions (31-33). We feel that this behavior is more compatible with the solvated redox polymer model than with the porous metal model.

The average charge per pyrrole unit in oxidized PP has been estimated a number of times (5,8,10-12). The films were removed from the preparation solution while at the preparation potential (ca. +0.8V vs SSCE), washed, dried and analyzed. The analyses correspond to one anion per 3 or 4 pyrrole units depending upon the anion. To estimate the number of pyrrole units in a PP film one should thus measure the charge under the voltammogram and divide by 3 or 4. However, the measured charge should include the "background" or "charging current" (except that due to the underlying electrode) up to the preparation potential (ca. +0.8V) since this additional charge also must lead to incorporation of anions into the film. This last conclusion is independent of the model used to describe the charging of the polymer film.

Niaz et al (8) indicate that they measured only the charge under the anodic peak and could not "account properly for the change in background current". Accordingly the measured charge (9% of preparation charge) corresponds to less than the expected 11% of the charge used to prepare the film. However, it is clear from the published voltammogram that if the anodic current is extrapolated to the preparation potential (+0.81V) the measured charge (ca. 16% of preparation charge) corresponds to significantly more than expected. Analysis of our results for PP in melts yields ca. 16% for Q_{cv}/Q_{prep} (where Q_{cv} is the average of anodic and cathodic charges under the cyclic voltammogram). This indicates that either more than one pyrrole unit in four is oxidized at E_{prep} or that less than 2 electrons per molecule are required for the polymerization. The latter is certainly likely since there must be end units which only need one electron. However, if this were the sole explanation, the average chain length would have to be three, which is unreasonable. Thus this analysis suggests that at +0.81V in CH_3CN and at +0.70V in the melt more than one pyrrole unit in four is oxidized.

The above discussion indicates that no reliable way of quantifying PP films has been found. For films prepared in molten $RuPyAlCl_4$ the problem is even greater because the films cannot be washed and dried with any confidence that the final product will be representative of the initially prepared film. From inspection of the voltammograms of Figures 2 and 3 it is clear that the charge under the voltammogram cannot accurately be measured as described above. It seems therefore that the best approach is to use the charge used to prepare the film as a relative measure of the quantity of film produced. As a rough conversion to film thickness we

assume that 240 mC/cm^2 yields a film 1 micron thick (4,13). We do this merely to allow some comparison with the literature on PP in CH_3CN .

Formal potential.

The discussion in the preceding section implies that PP does not have a unique E^0 . It is made up of many segments with different and multiple formal potentials.

In CH_3CN the " E^0 " of PP has been measured as the midpoint between E_{pa} and E_{pc} and found to be -220 mV vs SSCE (R) which translates to -330 mV vs the melt reference system (assuming ferrocene/ferricenium has the same formal potential in both solvent systems). Using this method for PP in melts we obtain the apparent formal potentials (E_{app}^0) shown in Table I. These show that in the melt the PP is oxidized and reduced at a potential slightly more positive than in CH_3CN and that there appears to be a slight dependence on melt basicity. The nature of the PP electrochemistry and the variable kinetics which influence the peak positions make E_{app}^0 a poor parameter from which to draw more complete conclusions.

Cyclic voltammetry in basic melt of PP films prepared in CH_3CN .

PP films on C and Pt electrodes were prepared at $+0.75 \text{ V}$ vs SSCE from 99% aqueous CH_3CN containing Et_4NClO_4 (0.1 M) and pyrrole (0.1 M). Figure 4A shows voltammograms in 0.8:1 melt and 0.1 M $\text{Et}_4\text{NClO}_4/\text{CH}_3\text{CN}$ of a Pt electrode coated with PP using 14 mC/cm^2 of charge. The potential axes have been aligned so that ferrocene would have the same E^0 in both solvents. The voltammogram in the melt was recorded first, then after washing the electrode well with CH_3CN the voltammogram in

CH₃CN was recorded. The charge used to prepare this film is a third of that (42 mC/cm²) used to prepare the film of Figure 3. It can be seen that the PP film made in CH₃CN does not function well in the melt, even after cycling (over 30 scans between -1V and +0.3V). Even in CH₃CN the voltammogram is not as sharp and symmetrical as that of the thicker film prepared and used in the melt (Figure 3). Thus PP films prepared and used in the melt exhibit more facile electrochemistry than those made in CH₃CN. This is especially noticeable and important for reduction of the film which is a problem in CH₃CN (8). The same conclusions result from experiments with PP on C electrodes.

Cyclic voltammetry in CH₃CN of PP films prepared in neutral melt.

Figure 4R shows cyclic voltammograms in 0.8:1 melt and in CH₃CN/Et₄NClO₄(0.1 M) of a Pt/PP (0.2 microns) electrode which was prepared in a neutral melt. The potential axes have been aligned so that ferrocene would have the same E⁰' in both solvents. The film was washed with toluene between preparation and use in 0.8:1 melt; it was then washed with toluene, acetonitrile and water and dried in air before use in CH₃CN.

The voltammogram of the PP film in the melt has more pronounced peaks than the voltammogram of the same film in CH₃CN. We take this as indicating that the redox chemistry of the film is more facile in the melt than in CH₃CN although the difference could possibly be due to thermodynamic factors. The differences in peak positions in Figure 4R is not regarded as significant given the variability of E_{app}⁰ (see tables 1 and 2).

Ferrocene electrochemistry at PP coated electrodes.

PP in its oxidised form represents a new class of electrode materials (7,8). Conducting organic materials are potentially useful electrode materials for organic electrochemistry. Another potential application of PP coatings is the modification of the electrochemical properties of inexpensive electrode materials such as nickel (40) so that such electrodes are useful for both analytical and synthetic electrochemistry. We have therefore investigated the electrochemistry of ferrocene at PP coated electrodes in basic and acidic melts.

Figure 5 shows the cyclic voltammetry of 130mM ferrocene in 0.8:1 melt at naked Pt and at Pt/PP (0.25 and 1.0 micron) electrodes. There is a large "charging current" in the region of the $\text{Fe}^{\text{III/II}}$ couple at the PP coated electrodes but the ferrocene wave is virtually unaffected. To decide whether the results of Figure 5 clearly show that the ferrocene reactions occur predominantly at the film-solution interface requires a comparison between the film thickness (d), the thickness of the diffusion layer (δ), the diffusion coefficient of ferrocene in the bulk solution (D_s) and in the polymer film (D_p) and the partition coefficient of ferrocene from the solution to the film (P) (R). Here the film non-conducting, the ferrocene electrochemistry would only be insensitive to the presence of the polymer if (41):

$$D_p P/d \gg D_s/\delta \quad (2)$$

In the present case $D_s = 4.8 \times 10^{-7} \text{ cm}^2 \text{ s}^{-1}$ (42), $\delta \sim 10^{-3} \text{ cm}$ (estimated from $(2D_s t)^{1/2}$ with $t = 1 \text{ s}$) and $d = 2.5 \times 10^{-5} \text{ cm}$ for the thinner film of Figure 5. Therefore, $D_p P$ would have to be greater than

$1.2 \times 10^{-8} \text{ cm}^2 \text{ s}^{-1}$ for the film to have no effect. This seems unreasonably high since there is no reason to expect that P is much greater than 1 and we have presented evidence that the mobility of the melt ions and hence presumably ferrocene is low in the polymer. Thus, we take the lack of a significant difference in the ferrocene wave at the three electrodes as indicating firstly that the PP films are conducting and have negligible resistance compared to the solution resistance and secondly that ferrocene electrochemistry takes place rapidly and reversibly at the PP/solvent interface. These results are consistent with the results obtained by other workers using CH_3CN (8,13).

In an acidic melt (1.2:1) the PP redox wave ($E^{0'} = -0.2\text{V}$) cannot be seen because the cathodic limit of the melt is ca. -0.3V . However, ferrocene ($E^{0'} = 0.27\text{V}$) electrochemistry in a 1.2:1 melt at a Pt/PP (0.17 microns) electrode is almost identical to that at naked Pt for the first few scans between 0 and +1V. On subsequent scans the wave broadens and the peak currents decrease.

These results show that PP may be a useful electrode material in ambient temperature molten salts. When oxidized it has excellent conductivity and its charge transfer rate to ferrocene in solution is fast in both acidic and basic melts. The origin of the stability problem in the acidic melt has not been determined.

Conductivity.

The cyclic voltammetry of PP prepared in the neutral melt suggests that the polymer is conducting when oxidized and non-conducting when

reduced. These conclusions are supported by the fact that ferrocene electrochemistry ($E^{0'} = 0.27V$) can be observed at the PP/melt interface but HCl electrochemistry ($E^{0'} \sim -0.5 V$ in 0.8:1 melt) cannot. HCl (from H_2O) is an impurity in all the melts used in this work and exhibits a quasi reversible redox wave at Pt electrodes. At thin film Pt/PP electrodes some reduction of HCl at Pt is observed as a membrane diffusion wave but there is no evidence for reduction at the PP/melt interface. There are two possible explanations for the inability of the PP film to reduce HCl. Either the reduced form of the polymer is non-conducting or the kinetics of HCl reduction on PP are very slow.

In order to estimate the conductivity of the PP prepared in the neutral melt a thick film of PP (ca. 20 microns) was grown on a Pt flag. The film was removed from the melt while still potentiostated at 0.85 V, washed with CH_3CN and water and dried in air. During this process the film noticeably shrank and peeled from the electrode. The resistance of the film was measured between two clips separated by ca. 2 cm. A rough estimate of the conductivity was $10^{-1} cm^{-1}$.

Summary of cyclic voltammetry of PP and conclusions.

Table 2 lists cyclic voltammetric data for a number of Pt/PP and C/PP electrodes in various melts and in CH_3CN . The term $\Delta i_p / Q_{prep}^v$ (where Δi_p is the difference between the peak anodic and cathodic currents and Q_{prep} is the charge used to prepare the film) should be constant and any variation should reflect kinetic limitations.

A number of important conclusions can be drawn from Table 2.

(a) For films thicker than 100 nm the kinetics of oxidation and

reduction influence the voltammetry at scan speeds as low as 20 mV/s. This appears as an increasing ΔE_p and a decreasing $\Delta i_p / \nu_{prep}^{1/2}$ with increasing scan speed or increasing film thickness.

(b) The 100 nm film on Pt appears to show no kinetic limitations up to 200 mV/s since ΔE_p is effectively constant. However, there is a residual ΔE_p which is presumably thermodynamic in origin (6). This thermodynamic ΔE_p must be lower in a 0.8:1 melt than in a 0.95:1 melt.

(c) PP electrochemistry is much more facile on Pt than on glassy carbon. This conclusion is also supported by other data not included in Table 2.

(d) The anodic wave is more susceptible to kinetic limitations than is the cathodic wave. Thus, as the scan speed or the film thickness is increased and ΔE_p increases, E_{pa} changes more than E_{pc} and so F_{app} moves to more anodic potentials.

(e) Films prepared in a neutral melt exhibit more facile electrochemistry in a 0.8:1 melt than in CH₃CN.

(f) Films prepared in CH₃CN show very poor electrochemistry in a 0.8:1 melt when compared to similar films prepared in the neutral melt. In CH₃CN they are similar to films prepared in the neutral melt.

(g) Peak positions are poorly reproducible. This is probably due to different degrees of swelling and hence variable kinetics and thermodynamics.

It should be noted that the differences between CH₃CN and the melt may be in part due to the different temperatures employed for experiments in the two solvents.

CONCLUSIONS

Polypyrrole films can be prepared in molten RuPyAlCl_4 and the electrochemistry of such films in 0.8:1 mole ratio $\text{AlCl}_3\text{:RuPyCl}$ melt appears to be more facile than that of PP films prepared in CH_3CN . The films prepared in the melt are conducting when oxidized and are potentially useful electrode materials. Their charge storing properties are superior to those of previously described PP films.

Further work concerning the nature of the electrochemical reaction of PP and the conductivity of films prepared in molten salts is in progress.

CREDIT

This work was supported in part by the Air Force Office of Scientific Research and the Office of Naval Research.

References

1. Murray, R. W., "Chemically Modified Electrodes", Chapter 3 in *Electroanalytical Chemistry*, Vol. 13, A. J. Bard, Ed., M. Dekker, New York, (in press).
2. Diaz, A. F.; Kanazawa, K. K.; Gardini, G. P., *J. Chem. Soc., Chem. Commun.*, 1979, 635.
3. Kanazawa, K. K.; Diaz, A. F.; Geiss, R. H.; Gill, W. D.; Kwak, J. F.; Logan, J. A.; Raholt, J. F.; Street, G. R., *J. Chem. Soc., Chem. Commun.*, 1979, 854.
4. Diaz, A. F.; Castillo, J. I., *J. Chem. Soc., Chem. Commun.*, 1980, 397.
5. Kanazawa, K. K.; Diaz, A. F.; Gill, W. D.; Grant, P. M.; Street, G. R.; Gardini, G. P.; Kwak, J. F., *Synthetic Metals*, 1979/80, 1, 329.
6. Diaz, A. F.; Crowley, J.; Rargon, J.; Gardini, G. P.; Torrance, J. R., *J. Electroanal. Chem.*, 1981, 121, 355.
7. Diaz, A. F.; Vasquez Vallejo, J. M.; Martinez Duran, A., *IRM J. Res. Develop.*, 1981, 25, 42.
8. Diaz, A. F.; Castillo, J. I.; Logan, J. A.; Lee, W.-Y., *J. Electroanal. Chem.*, 1981, 129, 115.
9. Watanabe, A.; Tanaka, M.; Tanaka, J., *Bull. Chem. Soc. Jpn.*, 1981, 54, 2278.
10. Salmon, M.; Diaz, A. F.; Logan, A. J.; Krounbi, M.; Rargon, J., *Mol. Cryst. Liq. Cryst.*, 1982, 83, 265.
11. Street, G. R.; Clarke, T. C.; Krounbi, M.; Kanazawa, K.; Lee, W.; Pfluger, P.; Scott, J. C.; Weiser, G., *Mol. Cryst. Liq. Cryst.*, 1982, 83, 253.
12. Tourillon, G.; Garnier, F., *J. Electroanal. Chem.*, 1982, 135, 173.
13. Bull, P. A.; Fan, F.-R. F.; Bard, A. J., *J. Electrochem. Soc.*, 1982, 129, 1009.
14. Genies, E. M.; Bidan, G.; Diaz, A. F., *J. Electroanal. Chem.*, 1983, 149, 101.
15. Feldberg, S., *J. Am. Chem. Soc.*, submitted; private communication.
16. Bredas, J. L.; Silbey, R.; Roudreaux, D. S.; Chance, R. R.; *J. Am. Chem. Soc.*, 1983, 105, 6555.

17. Frank, A. J.; Honda, K., J. Phys. Chem., 1982, 86 , 1933, and references therein.
18. Rurgmayer, P.; Murray, R. W., J. Am. Chem. Soc., 1982, 104 , 6139.
19. Rurgmayer, P.; Murray, R. W., J. Electroanal. Chem., 1983, 147 , 339.
20. Rurgmayer, P.; Murray, R. W., J. Am. Chem. Soc., submitted.
21. Bull, R. A.; Fan, F.-R.; Bard, A. J., J. Electrochem. Soc., 1983, 130 , 1636..
22. Pickup, P. G.; Osteryoung, R. A., J. Electrochem. Soc., 1983, 130 , 1965.
23. Chum, H. L.; Osteryoung, R. A., "Ionic Liquids", Inman, D.; Lovering, D. G., Eds., Plenum: New York, 1981, 407.
24. Robinson, J.; Osteryoung, R. A., J. Am. Chem. Soc., 1979, 101 , 323.
25. Gale, R. J.; Osteryoung, R. A., Inorg. Chem., 1979, 18 , 1603.
26. Karpinski, Z. J.; Osteryoung, R. A., Inorg. Chem., submitted.
27. Fannin, Jr., A. A.; King, L. A.; Levisky, J. A.; Wilkes, J. S., J. Phys. Chem., in press.
28. Tait, S.; Osteryoung, R. A., in preparation.
29. Lipsztajn, M.; Osteryoung, R. A., J. Electrochem. Soc., 1983, 130 , 1968.
30. Sahami, S.; Osteryoung, R. A., Anal. Chem., 1983, 55 , 1970.
31. Naum, P.; Murray, R. W., J. Phys. Chem., 1981, 85 , 389.
32. Kaufman, F. R.; Schroeder, A. H.; Engler, F. M.; Kramer, S. R.; Chambers, J. O., J. Am. Chem. Soc., 1980, 102 , 483.
33. Ikeda, T.; Schmehl, R.; Denisevich, P.; Willman, K.; Murray, R. W., J. Am. Chem. Soc., 1982, 104 , 2683.
34. Lipsztajn, M.; Osteryoung, R. A., Inorg. Chem., in press.
35. Hubbard, A.; Anson, F. C., Anal. Chem., 1966, 38 , 58.
36. Brown, A. P.; Anson, F. C., Anal. Chem., 1977, 49 , 1589.
37. Smith, D. F.; Willman, K.; Kuo, K.; Murray, R. W., J. Electroanal. Chem., 1979, 95 , 217.

38. Laviron, E., J. Electroanal. Chem., 1981, 122 , 37.
39. Pearce, P. J.; Bard, A. J., J. Electroanal. Chem., 1980, 114 , 89.
40. Bocarsly, A. R.; Galvin, S. A.; Sinha, S., J. Electrochem. Soc., 1983, 130 , 1319.
41. Gough, D. A.; Leyboldt, J. K., Anal. Chem. 1979, 51, 439.
42. Karpinski, Z. J.; Nanjundiah, C.; Osteryoung, P. A., in preparation.

Table 1. Apparent formal potentials for PP in neutral and basic melts

E_{app}' , mV vs. Al/Al(III) in 2:1 melt.

Substrate	Approx. film thickness, nm.	E_{app}' , mV vs. Al/Al(III) in 2:1 melt.	
		in 1:1 melt	in 0.80:1 melt
C	20	no anodic peak	-150
C	200	-160	-240
Pt	30	-240	-250
Pt	170	-200	-280
Average		-200	-230

TABLE 2. Cyclic Voltammetric Data For Polypyrrole Films (all potentials vs. Al/Al(III) in 2:1 melt).

Substrate	Q _{prep} , mC/cm ²	Approx. film thickness, nm.	Melt or Solvent	Scan rate, mV/s	E _{pa} , mV	E _{pc} , mV	E _{app} ⁰ , mV	ΔE _p , mV	Δi _p /Q _{prep}
Pt	25	100	0.95:1	40	-220	-350	-280	130	0.51
				80	-220	-330	-290	140	0.48
				200	-200	-330	-260	130	0.48
				400	-200	-350	-270	150	0.47
Pt	42	170	0.80:1	20	-240	-320	-280	80	0.66
				60	-220	-340	-280	120	0.61
				100	-230	-340	-290	110	0.60
				300	-190	-360	-280	170	0.56
				500	-170	-380	-280	210	0.53
				700	-130	-400	-270	270	0.51
C	48	200	0.80:1	5	-150	-330	-240	180	0.52
				20	-130	-380	-260	250	0.47
				60	-80	-420	-250	340	0.40
				100	-40	-450	-250	410	0.35
				300	+180	-590	-200	770	0.30
				500	+350	-690	-170	1040	0.27
Pt	239	1000	0.80:1	10	-90	-340	-220	250	0.44
C	7	31	0.80:1 CH ₃ CN ^b	100	-170	-330	-250	160	0.41
				100	-250	-350	-300	100	0.29
Pt	47	200	0.80:1 CH ₃ CN ^b	100	-230	-350	-290	120	0.45
				100	-140	-360	-250	220	0.32
^a Pt	14	58	0.80:1 CH ₃ CN ^b	100	-10	-310	-160	300	0.15
				100	-260	-360	-310	100	0.31
^a Pt	50	206	0.80:1 CH ₃ CN ^b	100	-90	-340	-210	250	0.06
				100	-260	-390	-330	130	0.10

(a) PP prepared in CH₃CN

(b) Potentials adjusted to melt reference system by comparison with ferrocene.

FIGURE LEGENDS

- Figure 1. Current vs. time profile for pyrrole polymerization at +0.7V (vs. Al/Al(III) in 2:1 AlCl₃:RuPyCl melt) onto a glassy carbon electrode from 0.17 M pyrrole in neutral AlCl₃:RuPyCl melt.
- Figure 2. Cyclic voltammetry of a C/polypyrrole (0.2 micron) electrode in neutral (A) and basic (0.8:1; B and C) AlCl₃:RuPyCl melts. Scan speed = 100 mV/s for A and B, 5 mV/s for C.
- Figure 3. Cyclic voltammetry as a function of scan speed for a Pt/polypyrrole (0.2 micron) electrode in 0.8:1 AlCl₃:RuPyCl melt.
- Figure 4. Cyclic voltammetry of Pt/polypyrrole electrodes in 0.8:1 AlCl₃:RuPyCl melt (—) and in 0.1 M Et₄NClO₄/CH₃CN (----). A, 0.06 micron PP film prepared in CH₃CN. B, 0.20 micron film prepared in neutral melt. Scan speed = 100 mV/s.
- Figure 5. Cyclic voltammetry of 130 mM ferrocene in 0.8:1 AlCl₃:RuPyCl melt at naked Pt (----) and at Pt/polypyrrole (0.25 micron, -.-.- and 1.0 micron —) electrodes. Scan speed = 100 mV/s.

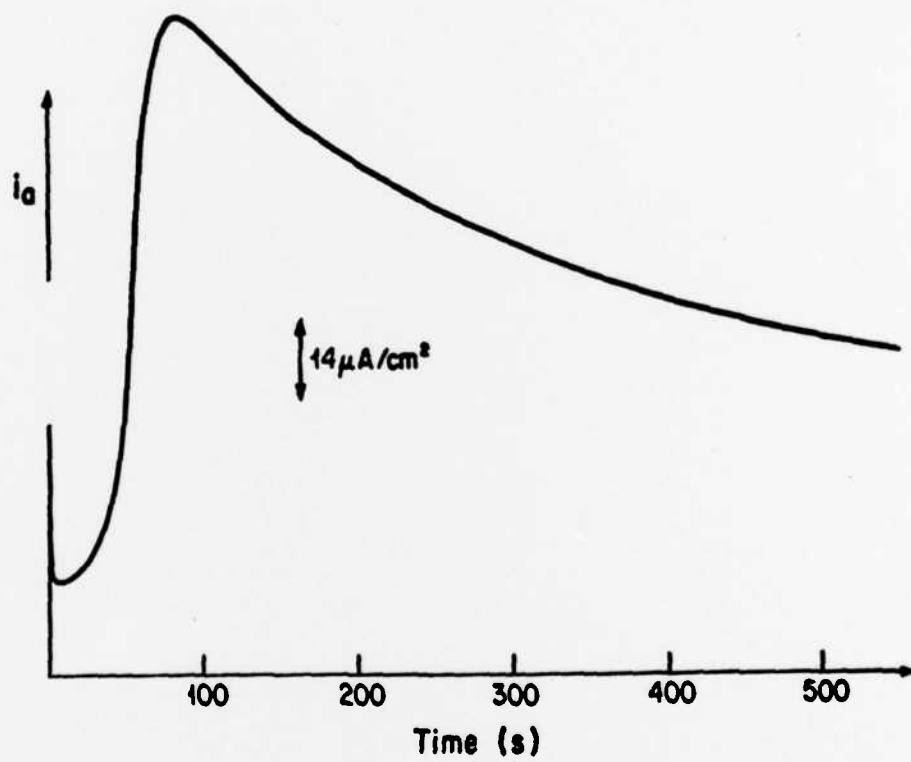


FIGURE 1

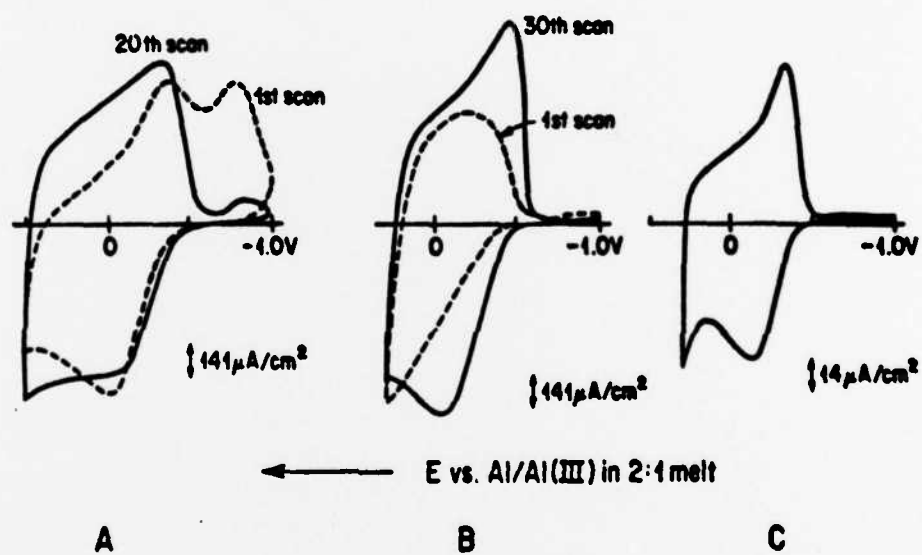


FIGURE 2

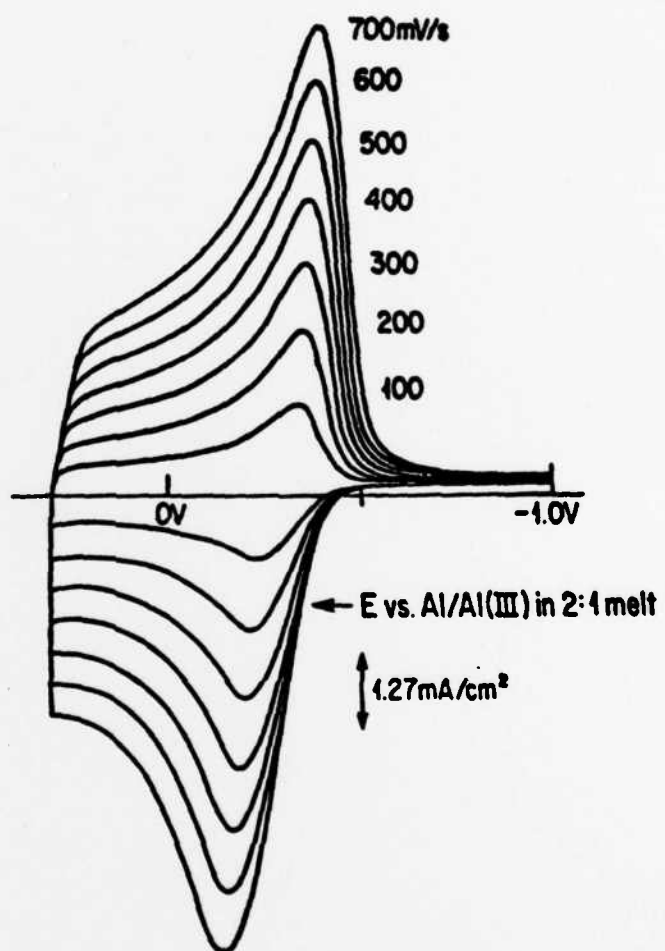


FIGURE 3

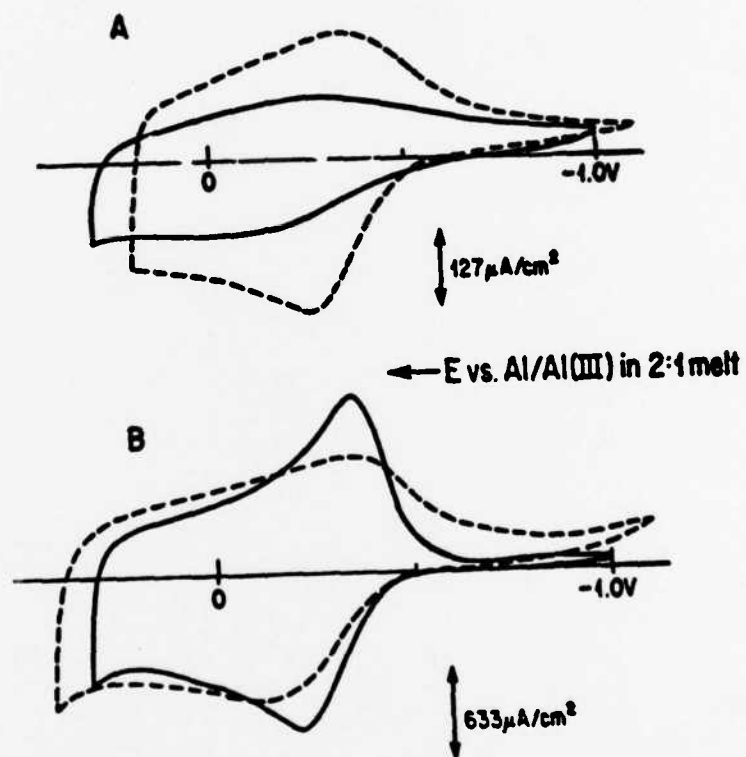


FIGURE 4

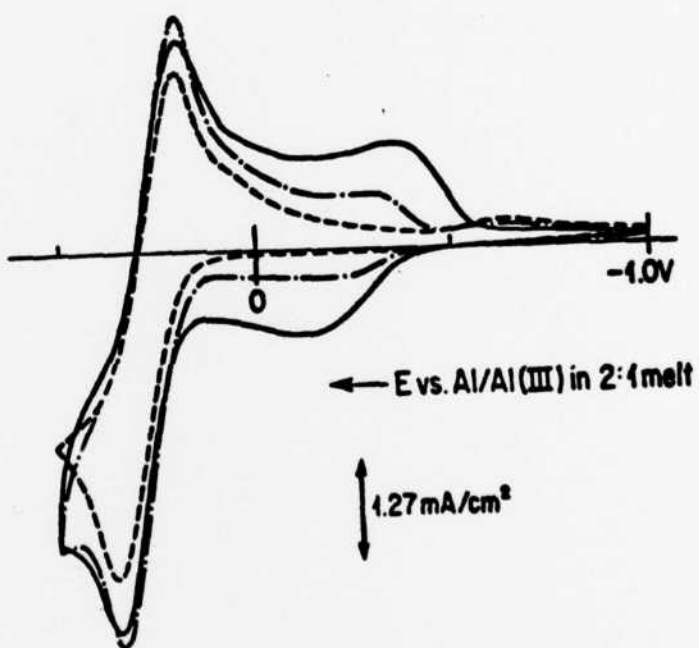


FIGURE 5

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 413 800 N. Quincy Street Arlington, Virginia 22217	2	Naval Ocean Systems Center Attn: Technical Library San Diego, California 92152	1
ONR Pasadena Detachment Attn: Dr. R. J. Marcus 1030 East Green Street Pasadena, California 91106	1	Naval Weapons Center Attn: Dr. A. B. Amster Chemistry Division China Lake, California 93555	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Washington, D.C. 20360	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1	Dean William Tolles Naval Postgraduate School Monterey, California 93940	1
Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Mr. Vincent Schaper DTNSRDC Code 2830 Annapolis, Maryland 21402	1
DTNSRDC Attn: Dr. G. Bosmajian Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1	Mr. A. M. Anzalone Administrative Librarian PLASTEC/ARRADCOM Bldg 3401 Dover, New Jersey 07801	1

TECHNICAL REPORT DISTRIBUTION LIST, 051B

Dr. M. B. Denton
Department of Chemistry
University of Arizona
Tucson, Arizona 85721

Dr. R. A. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. J. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. B. R. Kowalski
Department of Chemistry
University of Washington
Seattle, Washington 98105

Dr. H. Freiser
Department of Chemistry
University of Arizona
Tucson, Arizona 85721

Dr. H. Chernoff
Department of Mathematics
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139

Dr. A. Zirino
Naval Undersea Center
San Diego, California 92132

Professor George H. Morrison
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. Alan Bewick
Department of Chemistry
Southampton University
Southampton, Hampshire
ENGLAND SO95NA

Dr. S. P. Perone
Lawrence Livermore Laboratory L-370
P.O. Box 808
Livermore, California 94550

Dr. L. Jarvis
Code 6100
Naval Research Laboratory
Washington, D.C. 20375

Dr. G. M. Hieftje
Department of Chemistry
Indiana University
Bloomington, Indiana 47401

Dr. Christie G. Enke
Department of Chemistry
Michigan State University
East Lansing, Michigan 48824

Dr. D. L. Venezky
Naval Research Laboratory
Code 6130
Washington, D.C. 20375

Walter G. Cox, Code 3632
Naval Underwater Systems Center
Building 148
Newport, Rhode Island 02840

Professor Isiah M. Warner
Department of Chemistry
Emory University
Atlanta, Georgia 30322

Dr. Kent Eisentraut
Air Force Materials Laboratory
Wright-Patterson AFB, Ohio 45433

Dr. Adolph B. Amster
Chemistry Division
Naval Weapons Center
China Lake, California 93555

Dr. B. E. Douda
Chemical Sciences Branch
Code 50 C
Naval Weapons Support Center
Crane, Indiana 47322

Dr. John Eyler
Department of Chemistry
University of Florida
Gainesville, Florida 32611

TECHNICAL REPORT DISTRIBUTION LIST, 051B

Professor J. Janata
Department of Bioengineering
University of Utah
Salt Lake City, Utah 84112

Dr. J. DeCorpo
NAVSEA
Code 05R14
Washington, D.C. 20362

Dr. Charles Anderson
Analytical Chemistry Division
Athens Environmental Laboratory
College Station Road
Athens, Georgia 30613

Dr. Ron Flemming
B 108 Reactor
National Bureau of Standards
Washington, D.C. 20234

Dr. David M. Hercules
Department of Chemistry
University of Pittsburgh
Pittsburgh, Pennsylvania

Dr. Frank Herr
Office of Naval Research
Code 422CB
800 N. Quincy Street
Arlington, Virginia 22217

Professor E. Keating
Department of Mechanical Engineering
U.S. Naval Academy
Annapolis, Maryland 21401

Dr. M. H. Miller
1133 Hampton Road
Route 4
U.S. Naval Academy
Annapolis, Maryland 21401

Dr. Clifford Spiegelman
National Bureau of Standards
Room A337 Bldg. 101
Washington, D.C. 20234

Dr. Denton Elliott
AFOSR/NC
Bolling AFB
Washington, D.C. 20362

Dr. B. E. Spielvogel
Inorganic and Analytical Branch
P.O. Box 12211
Research Triangle Park, NC 27709

Ms. Ann De Witt
Material Science Department
160 Fieldcrest Avenue
Raritan Center
Edison, New Jersey 08818

Dr. A. Harvey
Code 6110
Naval Research Laboratory
Washington, D.C. 20375

Dr. John Hoffsommer
Naval Surface Weapons Center
Building 30 Room 208
Silver Spring, Maryland 20910

Mr. S. M. Hurley
Naval Facilities Engineering Command
Code 032P
200 Stovall Street
Alexandria, Virginia 22331

Ms. W. Parkhurst
Naval Surface Weapons Center
Code R33
Silver Spring, Maryland 20910

Dr. M. Robertson
Electrochemical Power Sources Division
Code 305
Naval Weapons Support Center
Crane, Indiana 47522

CDR Andrew T. Zander
10 Country Club Lane
ONR Boston
Plaistow, New Hampshire 03865

DL/413/83/01
0518/413-2

TECHNICAL REPORT DISTRIBUTION LIST, 0518

Dr. Robert W. Shaw
U.S. Army Research Office
Box 12211
Research Triangle Park, NC 27709

Dr. Marvin Wilkerson
Naval Weapons Support Center
Code 30511
Crane, Indiana 47522

Dr. J. Wyatt
Naval Research Laboratory
Code 6110
Washington, D.C. 20375

Dean William Tolles
Naval Post Graduate School
Spanaugel Hall
Monterey, California 93940

Dr. H. Wohltjen
Naval Research Laboratory
Code 6170
Washington, D.C. 20375

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. Paul Delahay
Department of Chemistry
New York University
New York, New York 10003

Dr. P. J. Hendra
Department of Chemistry
University of Southampton
Southampton SO9 5NH
United Kingdom

Dr. T. Katan
Lockheed Missiles and
Space Co., Inc.
P.O. Box 504
Sunnyvale, California 94088

Dr. D. N. Bennion
Department of Chemical Engineering
Brigham Young University
Provo, Utah 84602

Dr. R. A. Marcus
Department of Chemistry
California Institute of Technology
Pasadena, California 91125

Mr. Joseph McCartney
Code 7121
Naval Ocean Systems Center
San Diego, California 92152

Dr. J. J. Auborn
Bell Laboratories
Murray Hill, New Jersey 07974

Dr. Joseph Singer, Code 302-1
NASA-Lewis
21000 Brookpark Road
Cleveland, Ohio 44135

Dr. P. P. Schmidt
Department of Chemistry
Oakland University
Rochester, Michigan 48063

Dr. H. Richtol
Chemistry Department
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. E. Yeager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 44106

Dr. C. E. Mueller
The Electrochemistry Branch
Naval Surface Weapons Center
White Oak Laboratory
Silver Spring, Maryland 20910

Dr. Sam Perone
Chemistry & Materials
Science Department
Lawrence Livermore National Lab.
Livermore, California 94550

Dr. Royce W. Murray
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514

Dr. G. Goodman
Johnson Controls
5757 North Green Bay Avenue
Milwaukee, Wisconsin 53201

Dr. B. Brummer
EIC Incorporated
111 Chapel Street
Newton, Massachusetts 02158

Dr. Adam Heller
Bell Laboratories
Murray Hill, New Jersey 07974

Electrochimica Corporation
Attn: Technical Library
2485 Charleston Road
Mountain View, California 94040

Library
Duracell, Inc.
Burlington, Massachusetts 01803

Dr. A. B. Ellis
Chemistry Department
University of Wisconsin
Madison, Wisconsin 53706

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. M. Wrighton
Chemistry Department
Massachusetts Institute
of Technology
Cambridge, Massachusetts 02139

Dr. B. Stanley Pons
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112

Donald E. Mains
Naval Weapons Support Center
Electrochemical Power Sources Division
Crane, Indiana 47522

S. Ruby
DOE (STOR)
M.S. 6B025 Forrestal Bldg.
Washington, D.C. 20595

Dr. A. J. Bard
Department of Chemistry
University of Texas
Austin, Texas 78712

Dr. Janet Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Donald W. Ernst
Naval Surface Weapons Center
Code R-33
White Oak Laboratory
Silver Spring, Maryland 20910

Mr. James R. Moden
Naval Underwater Systems Center
Code 3632
Newport, Rhode Island 02840

Dr. Bernard Spielvogel
U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. William Ayers
ECD Inc.
P.O. Box 5357
North Branch, New Jersey 08876

Dr. M. M. Nicholson
Electronics Research Center
Rockwell International
3370 Miraloma Avenue
Anaheim, California

Dr. Michael J. Weaver
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. R. David Rauh
EIC Corporation
111 Chapel Street
Newton, Massachusetts 02158

Dr. Aaron Wold
Department of Chemistry
Brown University
Providence, Rhode Island 02192

Dr. Martin Fleischmann
Department of Chemistry
University of Southampton
Southampton SO9 5NH ENGLAND

~~Dr. R. A. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214~~

Dr. Denton Elliott
Air Force Office of Scientific
Research
Bolling AFB
Washington, D.C. 20332

Dr. R. Nowak
Naval Research Laboratory
Code 6130
Washington, D.C. 20375

Dr. D. F. Shriver
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Aaron Fletcher
Naval Weapons Center
Code 3852
China Lake, California 93555

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. David Aikens
Chemistry Department
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. A. P. B. Lever
Chemistry Department
York University
Downsview, Ontario M3J1P3

Dr. Stanislaw Szpak
Naval Ocean Systems Center
Loc 6343, Bayside
San Diego, California 95152

Dr. Gregory Farrington
Department of Materials Science
and Engineering
University of Pennsylvania
Philadelphia, Pennsylvania 19104

M. L. Robertson
Manager, Electrochemical
and Power Sources Division
Naval Weapons Support Center
Crane, Indiana 47522

Dr. T. Marks
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Micha Tomkiewicz
Department of Physics
Brooklyn College
Brooklyn, New York 11210

Dr. Lesser Blum
Department of Physics
University of Puerto Rico
Rio Piedras, Puerto Rico 00931

Dr. Joseph Gordon, II
IBM Corporation
K33/281
5600 Cottle Road
San Jose, California 95193

Dr. D. H. Whitmore
Department of Materials Science
Northwestern University
Evanston, Illinois 60201

Dr. Alan Bewick
Department of Chemistry
The University of Southampton
Southampton, SO9 5NH ENGLAND

Dr. E. Anderson
NAVSEA-56Z33 NC #4
2541 Jefferson Davis Highway
Arlington, Virginia 20362

Dr. Bruce Dunn
Department of Engineering &
Applied Science
University of California
Los Angeles, California 90024

Dr. Elton Cairns
Energy & Environment Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

Dr. D. Cipris
Allied Corporation
P.O. Box 3000R
Morristown, New Jersey 07960

Dr. M. Philpott
IBM Corporation
5600 Cottle Road
San Jose, California 95193

Dr. Donald Sandstrom
Department of Physics
Washington State University
Pullman, Washington 99164

Dr. Carl Kannewurf
Department of Electrical Engineering
and Computer Science
Northwestern University
Evanston, Illinois 60201

TECHNICAL REPORT DISTRIBUTION LIST, 359

Dr. Robert Somoano
Jet Propulsion Laboratory
California Institute of Technology
Pasadena, California 91103

Dr. Johann A. Joebstl
USA Mobility Equipment R&D Command
DRDME-EC
Fort Belvoir, Virginia 22060

Dr. Judith H. Ambrus
NASA Headquarters
M.S. RTS-6
Washington, D.C. 20546

Dr. Albert R. Landgrebe
U.S. Department of Energy
M.S. 68025 Forrestal Building
Washington, D.C. 20595

Dr. J. J. Brophy
Department of Physics
University of Utah
Salt Lake City, Utah 84112

Dr. Charles Martin
Department of Chemistry
Texas A&M University
College Station, Texas 77843

Dr. H. Tachikawa
Department of Chemistry
Jackson State University
Jackson, Mississippi 39217

Dr. Theodore Beck
Electrochemical Technology Corp.
3935 Leary Way N.W.
Seattle, Washington 98107

Dr. Farrell Lytle
Boeing Engineering and
Construction Engineers
P.O. Box 3707
Seattle, Washington 98124

Dr. Robert Gotscholl
U.S. Department of Energy
MS G-226
Washington, D.C. 20545

Dr. Edward Fletcher
Department of Mechanical Engineering
University of Minnesota
Minneapolis, Minnesota 55455

Dr. John Fontanella
Department of Physics
U.S. Naval Academy
Annapolis, Maryland 21402

Dr. Martha Greenblatt
Department of Chemistry
Rutgers University
New Brunswick, New Jersey 08903

Dr. John Wasson
Syntheco, Inc.
Rte 6 - Industrial Pike Road
Gastonia, North Carolina 28052

Dr. Walter Roth
Department of Physics
State University of New York
Albany, New York 12222

Dr. Anthony Sammells
Eltron Research Inc.
710 E. Ogden Avenue #108
Naperville, Illinois 60540

Dr. W. M. Risen
Department of Chemistry
Brown University
Providence, Rhode Island 02192

Dr. C. A. Angell
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. Thomas Davis
Polymer Science and Standards
Division
National Bureau of Standards
Washington, D.C. 20234

DATE
FILME

K33/281
5600 Cottle Road
San Jose, California 95193

and Computer Science
Northwestern University
Evanston, Illinois 60201

P.O. Box 3707
Seattle, Washington 98124

Washington, D.C. 20234

Dr. Robert Gotscholl
U.S. Department of Energy
MS G-226
Washington, D.C. 20545